

Chapter 8

Organic Solar Cells Modeling and Simulation

Mihai Razvan Mitroi

Polytechnic University of Bucharest, Romania

Laurentiu Fara

Polytechnic University of Bucharest, Romania & Academy of Romanian Scientists, Romania

Andrei Galbeaza Moraru

Polytechnic University of Bucharest, Romania

ABSTRACT

Modeling and simulation of organic (polymer, dye sensitized, and nanotube) solar cells is discussed. High J-V theoretical curves, the calculation of key parameters, and also the relative influence of different parameters on the cell operation, are evidenced and analyzed. On this basis, the authors obtain information on the optimization of the solar cell design and manufacturing.

MODELING AND SIMULATION OF ORGANIC CELLS BASED ON POLYMERS

Introduction

The polymer-based photovoltaic devices present some important advantages, such as the low cost and the easy manufacturing from thin films by chemical/physical vapour deposition, screen-printing, or casting. The band gap of the films can be adjusted by chemical synthesis to convenient values and the carrier mobility can reach $10 \text{ cm}^2/\text{V}\cdot\text{s}$ (Dimitrakopoulos & Mascaro,

2001; Kwok, 2003). Therefore, the polymer-based photovoltaic cells are competitive with those based on amorphous silicon, so that the interest for both the properties of the polymer materials and the characteristics of the polymer-based cells increases.

The first structure was a Schottky diode type structure, which has a conversion efficiency under 1%. In 1986, Tang (1986) introduced the planar donor-acceptor heterojunction, which has a higher conversion efficiency. Hiramoto, Fujiwara, and Yokoyama (1991) developed this idea. Tang introduced the concept of Bulk Heterojunction—BH. Xue et al. (2005) introduced the concept of Hybrid Heterojunction (HH) with higher efficiency 5%.


DOI: 10.4018/978-1-4666-1927-2.ch008

Solar cells based on organic polymers used photoinduced transfer of electrons from semiconductor polymers, donor / acceptor polymers or acceptor molecules (such as C_{60}). Pairs of layers polymer / fullerene have a poor conversion efficiency of solar cell. Nanomorphological control at nanoscale of the separate regions in an interlaced network (BH) significantly increased the conversion efficiency of solar energy cells made of MDMO-PPV/ C_{60} . Typical dimensions of the separate regions must be smaller than the exciton diffusion length. On the other hand, bicontinuous percolation paths for the transport of charge carriers at the electrodes must be provided in order to increase the transport of charge carriers in organic and polymeric materials, and for mesoscopic order to improve crystallinity. So, an interlaced network at nanoscale with crystalline order of the both constituents is formed (these ones belong to individual sub-networks). Such a network is a convenient structure for the active layer of polymer PV devices. At the same time, forbidden bands of the photoactive layer materials should be chosen in order to absorb more light in solar radiation spectrum.

Using a mixture of MDMO-PPV soluble fullerene derivative (for example PCBM), it is possible to obtain solar cells with a 2.5% conversion efficiency.

It was shown (Shaheen, et al., 2001) that a conversion efficiency of 2.5% (for AM 1.5) can be obtained using chlorobenzenes as a solvent for the deposition by centrifuging in the mass ratio of 1:4 for the MDMO-PPV:PCBM. Using chlorobenzenes instead of toluene nanomorphology changes were remarked and the efficiency conversion increases 3 times. Such BH solar cells contain 80% PCBM. However, the MDMO-PPV polymer could be the main light absorber from these solar cells, because PCBM does not achieve almost no absorption in the visible and near infrared region. So an increase in volume concentration of MDMO-PPV was necessary for a better absorption of sunlight.

Figure 1. Schematic representation of standard bulk heterojunction solar cell

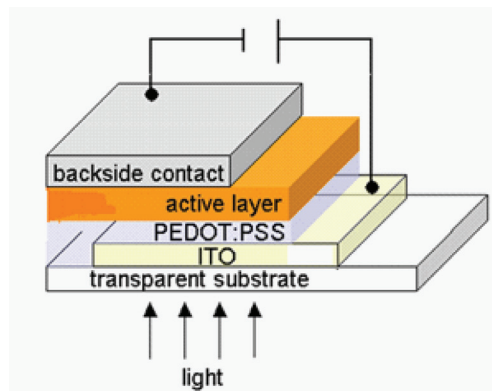

The electron mobility from pure PCBM is proved to be higher ($\sim 10^{-3} \text{ cm}^2/\text{Vs}$) compared to the holes mobility from the MDMO-PPV ($\sim 10^{-4} \text{ cm}^2/\text{Vs}$) and the holes mobility in the mixture increases with the increasing of fullerene mass, despite of the fact that the addition of fullerene introduces more defects (which would reduce the mobility).

By replacing in PCBM the C_{60} fullerene with C_{70} one, the HOMO-LUMO transition would be easier and would increase the absorption of light. An improved efficiency of BH solar cells in isomeric mixture of MDMO-PPV and C_{70} derivatives was obtained (Wienk, et al., 2003). Mixtures of this kind are suitable when they are prepared from a solution of o-dichlorobenzene (ODCB) and solar cells have a conversion efficiency of $\eta = 3 \%$ for PM 1.5.

Operating Principle of Polymer-Based Solar Cell

The process of conversion of light into electricity using an organic solar cell (Figure 1) can be plotted by the following steps: 1) absorption of a photon determining the formation of an excited state, that is, the creation of an exciton (electron-hole pair); 2) exciton diffusion to a region where dissociation occurs; 3) charge transport within the organic semiconductor to the respective electrodes.

16 more pages are available in the full version of this document, which may be purchased using the "Add to Cart" button on the publisher's webpage:
www.igi-global.com/chapter/organic-solar-cells-modeling-simulation/67765

Related Content

Logistic vs. W-Lambert Information in Quantum Modeling of Enzyme Kinetics

Mihai V. Putz and Ana-Maria Putz (2011). *International Journal of Chemoinformatics and Chemical Engineering* (pp. 42-60).

www.irma-international.org/article/logistic-lambert-information-quantum-modeling/50471

Modeling and Simulation of the Surface Topography Generation With Engineered Grinding Wheel

(2020). *Enhanced Heat Transfer Mechanism of Nanofluid MQL Cooling Grinding* (pp. 381-403).

www.irma-international.org/chapter/modeling-and-simulation-of-the-surface-topography-generation-with-engineered-grinding-wheel/247324

The Impact of Electrostatic Forces on the Dynamic and Heat Transfer Coefficient of Single Bubble Rising: Electrostatic Forces Effect on the Dynamic of Single Bubble Rising by CFD

Mohammad Ali Salehi and Samaneh Poursaman (2016). *International Journal of Chemoinformatics and Chemical Engineering* (pp. 35-46).

www.irma-international.org/article/the-impact-of-electrostatic-forces-on-the-dynamic-and-heat-transfer-coefficient-of-single-bubble-rising/177130

Optimization of Injection Molding Process Parameters via Design of Experiments: Medical Devices Environment

Karina Cecilia Arredondo-Soto, Arturo Realyvasquez-Vargas and Alejandro Jiménez-Zaragoza (2020). *Design of Experiments for Chemical, Pharmaceutical, Food, and Industrial Applications* (pp. 253-269).

www.irma-international.org/chapter/optimization-of-injection-molding-process-parameters-via-design-of-experiments/245597

The Structure, Topological, and Functional Dimension of Biomolecules

Gennadiy Vladimirovich Zhizhin (2016). *International Journal of Chemoinformatics and Chemical Engineering* (pp. 47-60).

www.irma-international.org/article/the-structure-topological-and-functional-dimension-of-biomolecules/177131