

Chapter 9

Super High Efficiency Multi-Junction Solar Cells and Concentrator Solar Cells

Masafumi Yamaguchi

Toyota Technological Institute (TTI), Japan

ABSTRACT

While single-junction solar cells may be capable of attaining AM1.5 efficiencies of up to 29%, Multi-Junction (MJ, Tandem) III-V compound solar cells appear capable of realistic efficiencies of up to 50% and are promising for space and terrestrial applications. In fact, the InGaP/GaAs/Ge triple-junction solar cells have been widely used in space since 1997. In addition, industrialization of concentrator solar cell modules using III-V compound MJ solar cells have been announced by some companies. This chapter presents principles and key issues for realizing high-efficiency MJ solar cells, issues relating to development and manufacturing, and applications for space and terrestrial uses.

INTRODUCTION

Multi-Junction (MJ, Tandem) solar cells are composed of multi-layers with different bandgap energies are shown in Figure 1 and have the potential for achieving high conversion efficiencies of over 50% and are promising for space and terrestrial applications due to wide photo response. Figure 2 shows theoretical conversion efficiencies of single-junction and Multi-Junction (MJ) solar cells in comparison with experimentally realized efficiencies.

Tandem solar cells were proposed by Jackson (1955) and Wolf (1960). Table 1 shows progress of the III-V compound multi-junction solar cell technologies. MIT group (Fan, Tsaur, & Palm, 1982) encouraged R&D of tandem cells based on their computer analysis. Although AlGaAs/GaAs tandem cells, including tunnel junctions and metal interconnectors, were developed in the early years, a high efficiency close to 20% was not obtained (Hutchby, Markunas, & Bedair, 1985). This is because of difficulties in making high performance and stable tunnel junctions, and the defects related to the oxygen in the AlGaAs

DOI: 10.4018/978-1-4666-1927-2.ch009

Figure 1. A schematic structure of a multi-layer solar cell


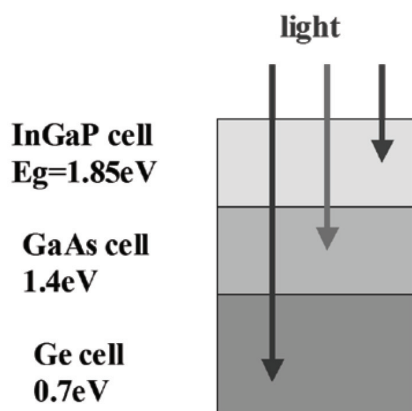


Figure 2. Theoretical conversion efficiencies of single-junction and multi-junction solar cells in comparison with experimentally realized efficiencies

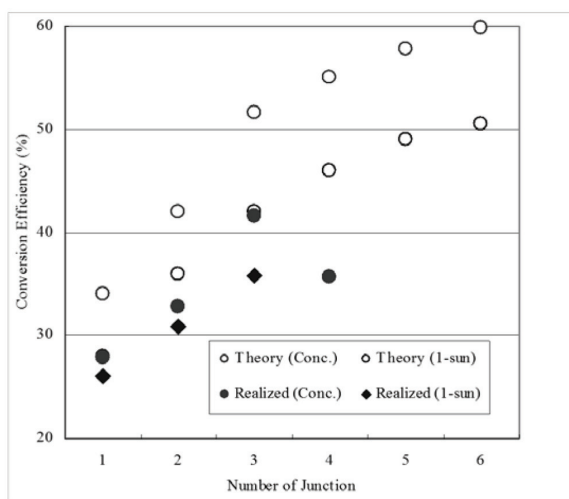

materials (Ando, Amano, Sugiura, et al., 1987). A Double Hetero (DH) structure tunnel junction was found to be useful for preventing diffusion from the tunnel junction and improving the tunnel junction performance by the authors (Sugiura, Amano, Yamamoto, & Yamaguchi, 1988). The authors demonstrated 20.2% efficiency AlGaAs/GaAs 2-junction cells (Amano, Sugiura, Yamamoto, & Yamaguchi, 1987). An InGaP material for the top cell was proposed by NREL group (Olson, Kurtz, & Kibbler, 1990). As a result of

performance improvements in tunnel junction and top cell, over 30% efficiency has been obtained with InGaP/GaAs 2-junction cells by the authors (Takamoto, Ikeda, Kurita, et al., 1997).

InGaP/GaAs-based MJ solar cells have drawn increased attention for space applications because superior radiation-resistance of InGaP top cells and materials have been discovered by the authors (Yamaguchi, Okuda, Taylor, et al., 1997). and those have the possibility of high conversion efficiency of over 30%. In fact, the commercial

22 more pages are available in the full version of this document, which may be purchased using the "Add to Cart" button on the publisher's webpage:

www.igi-global.com/chapter/super-high-efficiency-multi-junction/67766

Related Content

Optimization Design of Process Parameters for Different Workpiece Materials in NMQL Grinding With Different Vegetable Oils

(2020). *Enhanced Heat Transfer Mechanism of Nanofluid MQL Cooling Grinding* (pp. 337-357).

www.irma-international.org/chapter/optimization-design-of-process-parameters-for-different-workpiece-materials-in-nmql-grinding-with-different-vegetable-oils/247322

Catalyst for Biodiesel: An Overview of Catalysts Used in Biodiesel Production

Kapilan N. (2018). *Advanced Solid Catalysts for Renewable Energy Production* (pp. 156-175).

www.irma-international.org/chapter/catalyst-for-biodiesel/196149

Graph-Theoretical Indices based on Simple, General and Complete Graphs

Lionello Pogliani (2011). *International Journal of Chemoinformatics and Chemical Engineering* (pp. 12-28).

www.irma-international.org/article/graph-theoretical-indices-based-simple/50469

Photocatalytic Activity of ZnO Nanoparticles on the Degradation of Organic Dyes Under Solar Light

Sivakumar Krishnamoorthy and Dharani M. (2020). *Handbook of Research on Emerging Developments and Environmental Impacts of Ecological Chemistry* (pp. 409-431).

www.irma-international.org/chapter/photocatalytic-activity-of-zno-nanoparticles-on-the-degradation-of-organic-dyes-under-solar-light/251593

Long Destruction of Structurally Damaged Composite Pipe

Akhundov Mohammed B. and Sadayev Azber Sh. (2013). *International Journal of Chemoinformatics and Chemical Engineering* (pp. 37-47).

www.irma-international.org/article/long-destruction-structurally-damaged-composite/75222